

DA A124 934


MOISTURE CONTENT OF WOOD IN USE REVISION(C) FOREST
PRODUCTS LAB MADISON WI 1973 FSRN-FPL-0226

1/1

UNCLASSIFIED

E/G 11/12 • NL



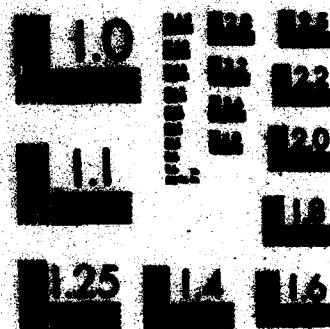

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS-1963-A

AD A124934

U.S. DEPARTMENT OF AGRICULTURE - FOREST SERVICE
FOREST PRODUCTS LABORATORY - MADISON, WIS.

U.S.D.A. FOREST SERVICE
RESEARCH NOTE
FPL-0226
1973

MOISTURE CONTENT OF WOOD IN USE¹

Forest Products Laboratory,² Forest Service
U.S. Department of Agriculture

DTIC
ECTE
FEB 25 1973

Summary

The moisture content of wood will change with changes in the conditions under which it is used. To give best service, the wood should be installed at a moisture content close to the midpoint between the high and low values it will usually attain in use. This report presents recommendations that will enable the user to select the preferable moisture content for wood used under various conditions.

Introduction

Wood products shrink as they dry and swell as they absorb moisture, either liquid or vapor, from the atmosphere. Unless these changes in dimension are kept to a minimum, they may result in unsatisfactory service of wood products and structures.

Fortunately, most of the difficulties caused by moisture can be practically eliminated by drying the wood—to the moisture content best suited for the intended use—before the wood is put into service. The optimum moisture content will be midway between the extreme values that the wood is likely to reach.

If the wood is too wet when it is put into place, it will eventually dry to a moisture content approximating that of the conditions under which it is used. This drying in place will be accompanied by shrinkage.

In a house, this shrinkage may cause loosening of fastenings and settling of the building with resulting plaster cracks, drywall nail popping, and unsightly openings around trim and moldings. Excessive shrinking of studs, sheathing, and siding decreases the weathertightness of walls, loosens fastenings, and may reduce the mechanical stiffness of walls.

If wood is dried too far below the average moisture content it will reach in use, swelling may cause drawers, windows, and doors to stick.

¹Revision of Forest Products Laboratory report 1655, of the same title, originally written in 1947 by E. C. Peck.

²Maintained at Madison, Wis., in cooperation with the University of Wisconsin

88 02 023 099

DTIC FILE COPY

A moisture, weight, density, and other tests have been made on green lumber and timber to determine the effect of drying on the wood. The results of these tests are given in this report.

Shrinkage and swelling are also given. The shrinkage and swelling of green lumber and timber are given in this report. The shrinkage and swelling of green lumber and timber are given in this report.

This report summarizes information and recommendations that will help the user select the correct moisture content.

Green Lumber and Timber

Green lumber, dimension, and timber are best used under conditions where the wood is maintained at a high moisture content or where shrinkage and swelling caused by drying in place have been considered in the design of the structure.

It may be feasible, for example, to use green timber for piling that is submerged in water or for large members of wood boats.

Large timbers that would require an exceedingly long and mild seasoning period to dry without serious seasoning defects are generally used green and allowed to season in place. Such timbers are used in construction of bridges, trestles, and mill buildings where shrinkage, splits, checks, and other drying defects have been considered in the design of the structure. Also, at present, many large timbers are fabricated from several laminations of dried 1-inch or 2-inch lumber banded together. The dried laminations permit the producer to control final moisture content quite accurately, and this minimizes many of the moisture content problems associated with the use of green timbers.

The greatest difficulty connected with the use of green, untreated lumber and timber is decay, particularly at joints and contact points.

Air-Dried Lumber and Dimension

In most parts of the country, the minimum moisture content that can be generally obtained in air drying is about 12 to 15 percent. Most air-dried material is usually closer to 20 percent moisture content when used.

Air-dried lumber is suitable for items that are not ordinarily subjected to the artificial heat and dehumidification of buildings or where appreciable shrinkage can be tolerated. All types of out-buildings, such as sheds and barns, can usually be safely constructed of air-dried lumber. Air-dried lumber is also satisfactory for products used outdoors, such as boxes and crates, parts of agricultural implements, and truck and trailer bodies.

Kiln-Dried Lumber and Dimension

Kiln-dried lumber or air-dried lumber that has received additional drying in a heated room is recommended for all uses that require a moisture content below about 12 percent. In most parts of the United States this will include practically all interior woodworking, such as flooring, trim, furniture, stairway stock, panels, and cabinet work that is used inside heated buildings.

Figure 1 is a graph showing the relationship between the moisture content of lumber and the relative humidity of the air in which it is used. It is a useful guide in selecting the proper moisture content of lumber for use in various localities. The graph shows that the moisture content of lumber should be adjusted to the relative humidity of the air in which it is used. For example, lumber should be seasoned for use in New Orleans, for example, should not be seasoned for use in Minneapolis; a door manufactured in Wisconsin of kiln-dried lumber would probably undergo troublesome swelling and warping if it were shipped to the relatively humid conditions of Galveston, Texas.

Table 1, which is given in Figure 2, shows the recommended moisture content of lumber and other wood products for use in various localities. It is a useful guide in selecting the proper moisture content of lumber for use in various localities. The table shows that the moisture content of lumber should be adjusted to the relative humidity of the air in which it is used. For example, lumber should be seasoned for use in New Orleans, for example, should not be seasoned for use in Minneapolis; a door manufactured in Wisconsin of kiln-dried lumber would probably undergo troublesome swelling and warping if it were shipped to the relatively humid conditions of Galveston, Texas.

Although the values in the tables and figures are averages first developed in the 1930's, their accuracy and workability have been verified by numerous investigations since then. They provide a sound basis for selecting the correct moisture content of wood for use under the various conditions.

If recommendations given in table 1 and in the following paragraphs are observed, most difficulties connected with the use of improperly seasoned lumber will be eliminated.

Plywood, Particleboard, and Hardboard

Plywood, particleboard, hardboard, and other more extensively processed wood products undergo a significant change in hygroscopicity during manufacture. Frequently the desired equilibrium moisture content of such materials is not known. In such cases, the material should be conditioned to approximate equilibrium with the proper relative humidity shown in figure 3. It is not desirable to condition such products to the same moisture content as lumber.

Recommendations

1. Use lumber that is dried to a moisture content close to the midpoint between the high and low values the wood will attain in service. Table 1 and figure 3 show the recommended moisture content values for wood used in interior and exterior parts of heated buildings. The values for exterior sheathing and trim will also apply to lumber used outdoors and in unheated buildings.

2. If it is not known beforehand in what locality a product will be used, the wood should be dried to a moisture content of about 6 percent, which is close to the average of the values preferred for the arid and damp regions.

3. In most of the United States, practically all interior woodwork, such as trim, flooring, panels, and cabinet work, should be kiln-dried. Material for furniture, cabinets, case goods, musical instruments, tool handles, turning stock, and sporting goods should be kiln dried to an average moisture content between 5 and 6 percent.

4. Air-dried lumber is suitable for items that are not ordinarily subjected to artificial heat or for use in structures in which some shrinkage can be tolerated.

Table 1.--Recommended moisture content values for various wood items at time of installation

Use of wood	Moisture content for--					
	West areas of United States ¹		Dry southwestern area		Damp, warm coastal areas ¹	
	Average ²	Individual pieces	Average ²	Individual pieces	Average ²	Individual pieces
	Pct.	Pct.	Pct.	Pct.	Pct.	Pct.
Interior:						
Woodwork, flooring						
Furniture, wood trim	8	6-10	6	4-9	11	8-13
Laminated timbers						
Exterior:						
Siding, wood trim						
Framing, sheathing	12	9-14	9	7-12	12	9-14
Laminated timbers						

¹For limiting range, see figure 3.

²To obtain a realistic average, test at least 10 pct. of each item. If the amount of a given item is small, several tests should be made. For example, in an ordinary dwelling having about 60 floor joists, at least 10 tests should be made on joists selected at random.



Accession For	
DTIC GRAAI	<input checked="" type="checkbox"/>
DTIC TAB	<input type="checkbox"/>
Unannounced	<input type="checkbox"/>
Justification	
By	
Distribution/	
Availability Codes	
Avail and/or	
Dist	Special
A	

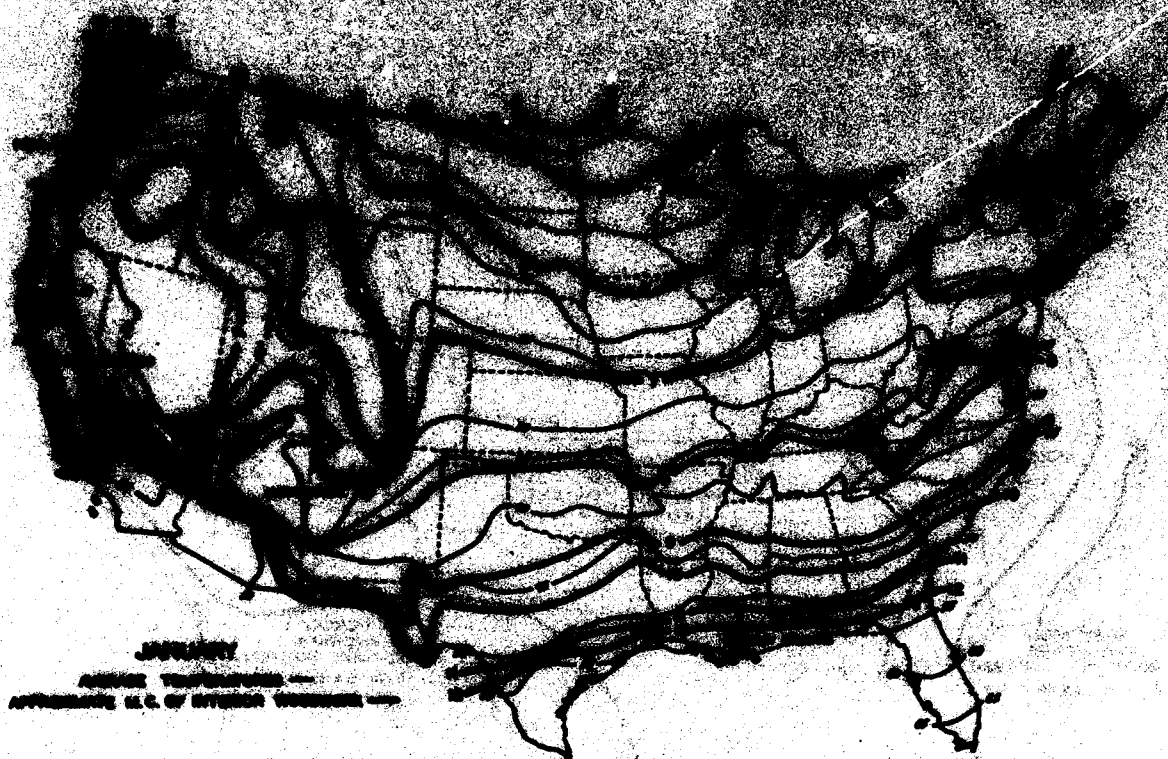


Figure 1.--Relation of moisture content of interior woodwork to outdoor temperature of various areas of the United States in January. M 16876F

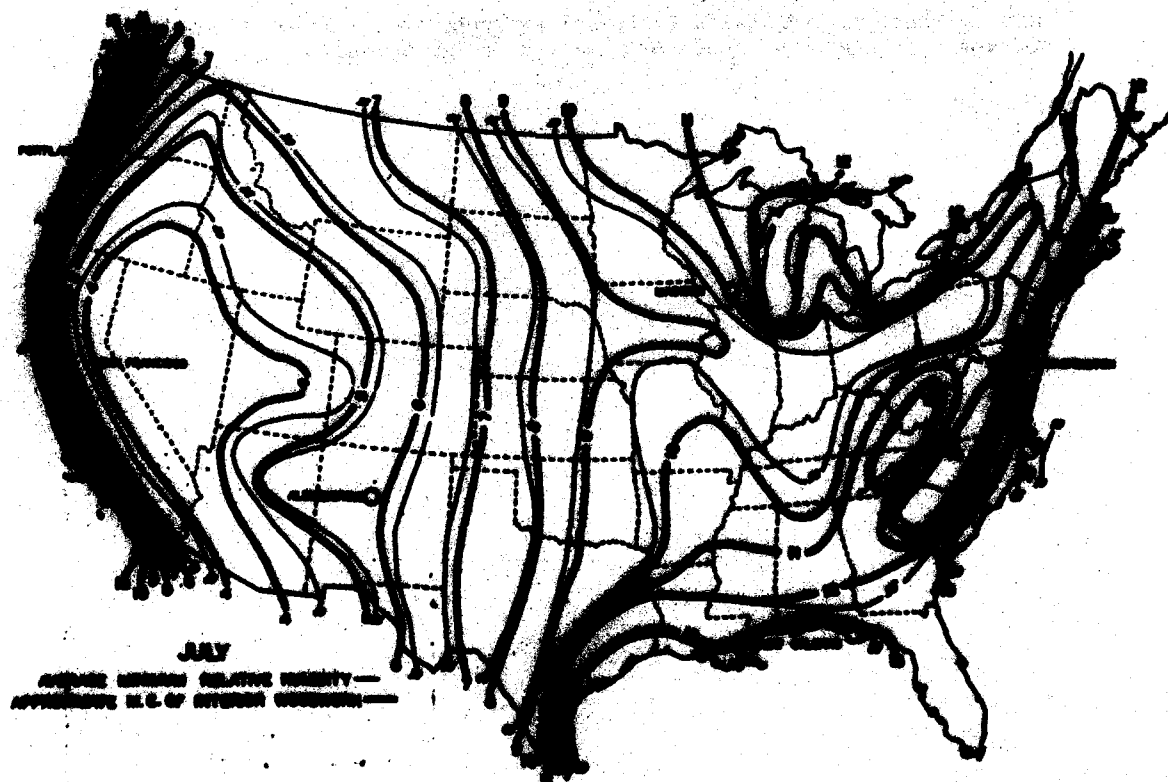


Figure 2.--Relation of moisture content of interior woodwork to outdoor relative humidity of various areas of the United States in July. M 16877F

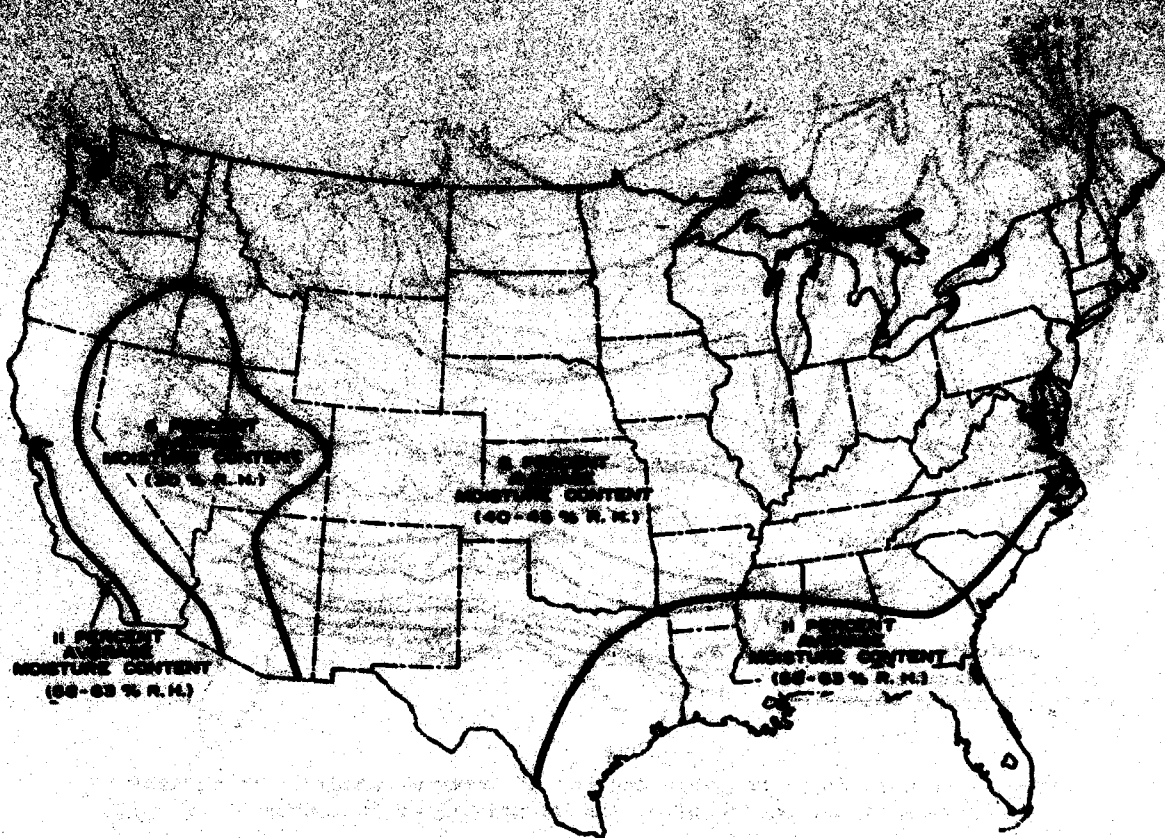


Figure 3.--Recommended moisture content averages for interior-finishing woodwork for use in various parts of the United States.

134 757